

# Analysis of Normal Zone Propagation in Pancake-shaped Nb<sub>3</sub>Sn Superconducting Magnet

Qiuliang Wang, Jinliang He, Cheon Seog Yoon, Keeman Kim, Zheng Nam

**Abstract**— A quench phenomenon is caused by an external disturbance in a superconducting magnet, where the magnet is operating in a cryogenic environment. The heat coupling between the layers and pancakes of the magnet can induce the normal zone propagation with fast speed. In order to analyze quench behavior in a pancake-shaped superconducting magnet, a quasi-three-dimensional model is proposed. A moving mesh finite volume method is employed in solving the heat conduction equation. The quench process of the superconducting magnet is studied under the various operating conditions and cooling conditions.

**Index Terms** -- pancake-shaped magnet, moving mesh method.

## I. INTRODUCTION

A superconducting magnet is disturbed by local dissipation of energy due to the conductor motion, epoxy-resin crack and ac loss etc.. Such a disturbance can induce a local temperature rise. When the temperature rise is attained to the critical temperature of the superconductor, a normal zone is formed. Quench results in the normal zone spread to the whole superconducting magnet and the damage of the magnet and cryogenic system in serious case. Stability and quench characteristics are two essential aspects of designing superconducting magnet system. The magnet system should be designed against the permanent damage caused by overheating, overstressing, and arcing that may stem from quench. Hence, the considerable amount of attention has been paid to the study of the problem. Because the superconducting magnet has a three-dimensional structure, the heat coupling occurs between the layers and pancakes. If the external disturbance is enough to quench the superconducting magnet, a normal zone propagates through the layers and pancakes. The heat is conducted to radial, axial, and azimuthal directions of the magnet. Although the approximation of high normal zone propagation speed in the azimuthal direction was adapted to analyze the small-scale superconducting magnet [1]. Generally, it is not used for the analysis of the large bore

superconducting magnets and the high temperature superconducting magnet with small hole. The 3-dimensional heat conduction problem should be employed to study quench phenomena. The work presented here is to study quench characteristics in a pancake-shaped superconducting magnet system in various operating conditions and disturbances. A quasi-three-dimensional model is used. The heat conduction is along the superconducting wire and the heat coupling is between the layers and pancakes of the superconducting magnet. A quench propagation problem is a moving boundary problem. A moving mesh finite volume method is used to solve the problem in order to obtain high accuracy of numerical simulation [2].

## II. PHYSICAL MODEL AND MOVING MESH METHOD

A pancake-shaped superconducting magnet is studied. The superconducting magnet consists of several pancake-shaped coils where the heat coupling occurs between pancakes and layers in the coils. The temperature is assumed to be uniform in the cross-section of the superconducting wire. The thermal conductivity of the insulation film is much smaller than that of the metal in the composite, therefore, the conduction of insulation along the superconducting wire is ignored in the analysis. If a superconducting magnet is subjected to a heat disturbance, the temperature ( $T$ ) distribution is determined by following equation

$$\gamma C \frac{\partial T}{\partial t} = \frac{\partial}{\partial x} \left( k \frac{\partial T}{\partial x} \right) + s(T_c, x, t) + Q_d - \sum_i \frac{P_i h_i}{A} (T - T_i) \quad (1)$$

where  $t$  and  $x$  denote the time and space coordinates, respectively,  $\gamma C$  is the average heat capacity of superconductor, stabilizer and insulators,  $Q_d$  is the external disturbance power,  $A$  is the cross-sectional area of superconducting wire,  $P_i$  and  $h_i$  are the contact perimeter and heat transfer coefficient between layers or pancakes, respectively. The Joule heat power is given by

$$s(T, T_c, x, t) = \rho J^2 H(T - T_c) \quad (2)$$

where  $J$  and  $\rho$  are the current density and resistivity of the stabilizer, and  $H(T-T_c)$  is a Heaviside-like transition function from the superconducting regions,  $T_c$  is the critical temperature of superconductor.

The heat generated due to the quench flows, not only along the superconducting wires, but also in transverse direction, through the insulation. Within the pancake-shaped magnet, this tends to short-circuit the quench propagation along the conductor causing the pre-heating and birth of normal zones

Manuscript received September 17, 2000. This work was supported by the Korean Ministry of Science & Technology.

Qiuliang Wang is with the Samsung Advanced Institute of Technology, 103-6 Moonji-dong, Yusong-Gu Taejon Korea and Institute of Electrical Engineering, Academia Sinica (telephone: 82-42-865-4401, e-mail: qlwang@venus.sait.samsung.co.kr).

C.S. Yoon is with the Department of Mechanical Engineering, Hannam University, Taejon, Korea. (e-mail: csyoon@eve.hannam.ac.kr).

K. Kim is with the Samsung Advanced Institute of Technology, Taejon 305-380, Korea (telephone: 82-42-865-4409).

J.L.He is with the Electrical Engineering Department, Tsinghua University, Beijing, China.

Z. Name is with the Department of Physics, Huazhong University of Science and Technology, Wuhan, 430074, P.R. China.

in the adjacent layers. Furthermore, the heat conduction will initiate the quench in the adjacent pancakes. The heat coupling term is treated as an external heat source. Therefore, the approximation of the heat transfer in the winding pack is obtained by substituting each part of wire and insulation between two conductors with an equivalent slab having the same average extension in the direction normal to heat flux. By the simplification, the heat diffusion in the winding cross-section can be regarded as a set of independent one-dimensional problems. The 3-dimensional problem is reduced to one-dimensional model. The heat transfer coefficient between the pancakes or layers is calculated by the steady state temperature distribution across the superconducting wire, insulation, and other superconducting wire. The heat transfer coefficient is varied with the average temperature of the cross section of superconducting wire and insulation [3].

When the superconducting magnet is quenched, the normal zone is propagating. The front position of normal zone, where is the boundary of Joule heat generated, is moving and the front region is very short in the lengthwise. In order to obtain the converged numerical solution, the mesh size in the front region of normal zone should be finer and other region of the solution domain might be coarser. For a long length of wire, the finite mesh number is necessary. Therefore, moving mesh finite volume method has more advantages and is applied for this problem. For the one-dimensional moving mesh equation can be given [4]

$$\frac{\partial^2}{\partial \xi^2} \left( M \frac{dx}{dt} \right) + \frac{1}{\tau} \frac{\partial}{\partial \xi} \left( M \frac{\partial x}{\partial \xi} \right) = 0 \quad (3)$$

where  $\tau$  is the mesh smoothing parameters,  $\xi$  is the equal interval coordinate,  $M$  is the monitor function. Since smoothing monitor function is more straightforward to apply than smoothing mesh concentration, the technique is employed here. The equation (1) is rewritten in the Lagrangian form:

$$\gamma C \frac{\partial T}{\partial t} - \gamma C \frac{dx}{dt} \frac{\partial T}{\partial x} = \frac{\partial}{\partial x} \left( k \frac{\partial T}{\partial x} \right) + s(T, T_c, x, t) + Q_d - \sum_i \frac{P_i h_i}{A} (T - T_i) \quad (4)$$

The space of the equations (3) and (4) can be discretized by using finite volume method. The semi-discretization of the equation is the stiff ordinary differential-algebraic equation. The helium heat transfer for bath temperature  $T_b$  is

$$q_h = \begin{cases} 1.2 \times 10^4 (T - T_b) & (T - T_b \leq 0.58) \\ 1.05 \times 10^4 - 6 \times 10^3 (T - T_b) & (0.58 < T - T_b \leq 1.5) \\ 1.2 \times 10^3 + 2.3 \times 10^2 (T - T_b) & (1.5 < T - T_b) \end{cases} \quad (5)$$

TABLE-I  
PARAMETERS OF 3-PANCAKE-SHAPED MAGNET SYSTEM

Symbol	Quantity	Symbol	Quantity
Inner diam.	30 cm	Outer diam.	85 cm
Height	1.5 cm	Field	6.5-12.5 T
Operating current	1.1-3.1 kA	Bathe temperature	4.2 K
Size of tape	1.5 mm x 5 mm	Area of Cu	5 mm <sup>2</sup>
Area of Nb <sub>3</sub> Sn	2.5 mm <sup>2</sup>	Insulator thickness	50 μm

### III. RESULTS AND DISCUSSION

The numerical simulation results are presented in this part. A 3-pancake-shaped magnet and 1-pancake-shaped magnet are assumed to be located at the uniform background field. The background field includes the external field and self-field of magnet. Generally, the background field can be obtained by adjusting the external field to make the field to be uniform. Finally, the influence of self-field on normal zone propagation is studied by a 6-pancake-shaped magnet with the external field of 0 T.

The 3-pancake superconducting magnet wound by continuous superconducting wire and surrounded by liquid helium is located in the background field of 12.5 T and operating current of 1.1 kA. The heat disturbance with duration of 5 ms and length of 0.15 m is applied to 17<sup>th</sup> layer of the pancake-2. The main parameters of the magnet are listed in the Table-I. Fig. 1 illustrates the hot-spot temperature rise versus time for insulation thickness  $d_{ins} = 25, 20$  and  $12.5 \mu\text{m}$  with the disturbance over than their minimum quench energy. The hot spot temperature of insulation thickness of  $25 \mu\text{m}$  is over than that of  $12.5 \mu\text{m}$ . The heat coupling term between the layers and pancakes depends on the equivalent heat transfer coefficient. The thicker insulation results in a lower heat transfer between layers and pancakes. Therefore, during local quench of the pancake, the transfer of Joule generating heat and disturbance from the disturbance center to the lower temperature region of the superconducting magnet is more difficult. It leads to the high hot spot temperature. Fig.2 shows the profiles of the normal zone length versus time. The high hot-spot temperature makes the normal zone increased with relatively fast speed along the superconducting wire. Fig.3 illustrates the temperature distribution in the insulation thickness of  $25 \mu\text{m}$  for pancakes 1, 2 and 3. The origin of coordinate is located at the outer radius of the No.1 pancake. It shows that the heat coupling between the layers and pancakes is very strong. The heat diffusion between layers or pancakes can result in the adjacent layers or pancakes quench.

The influence of operating current on the normal zone propagation is studied by the 1-pancake-shaped magnet with the inner radius of 30 cm and outer radius of 85 cm. The parameters of tape of Nb<sub>3</sub>Sn are listed in Table-I. Fig 4 shows the normal zone profiles for the operating currents of 1.1, 2.1 kA and background field of 8.5 T. Comparing the magnet operated at 1.1 kA and 2.1 kA, the extension of the normal zone for operated at 2.1 kA is much faster than that of 1.1 kA due to the large Joule heating generation power. Because of the temperature difference between hot spot and lower temperature region in the same layer, the temperature distribution is wave-shaped along the length of Nb<sub>3</sub>Sn superconducting wire. Fig.5 illustrates the hot-spot temperature versus time. The higher operating current induces a higher hot-spot temperature. The low operating current generates a relative long relaxation time for the quench process of the magnet. From the Fig.5, at first, the hot-spot temperature for operating current of 1.1 kA increases slowly

and then it increases fast. When the hot-spot temperature is over than the current sharing temperature, the Joule heat is generated in the layer disturbed when the adjacent layers are still in the superconducting state. Most heat flow is conducted along the superconducting wire. With the increasing the hot-spot temperature, the transverse heat flux is increased and then the layer disturbed and its adjacent layers start into the normal state or current sharing state, the Joule heat increases with very fast speed so that the hot-spot temperature is fast increased.

The influence of the heat transfer of liquid helium is studied. The parameters of the 1-pancake-shaped magnet are the same as above. The disturbance is located at 22<sup>th</sup> layer of the pancake-shaped magnet with the disturbance length of 0.15 m and duration time of 5 ms, background field of 8.5 T and operating current of 3 kA. The heat transfer coefficients are set as  $h = 0, 1500, 3000 \text{ W/m}^2$  and the value based on the equation (5). The hot spot temperature versus time is shown in Fig.6. The lower heat transfer coefficient can generate the higher hot-spot temperature rise. The hot-spot temperature for the heat transfer calculated based on equation (5) is higher than that of  $h = 3000 \text{ W/m}^2$  after about  $t=10.5 \text{ ms}$ . The transient heat transfer of liquid helium is varied with the temperature difference  $\Delta T = T - T_b$ . When the temperature difference is over that about 20 K, the heat transfer calculated based equation (5) is lower than that with  $h = 3000 \text{ W/m}^2$

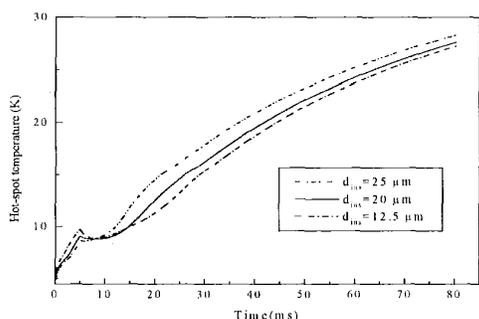


Fig.1 Hot-spot temperature rise of 3-pancake-shaped magnet system versus time.

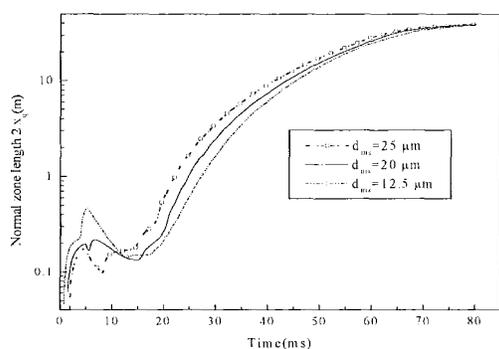


Fig.2 Profiles of normal zone length of 3-pancake-shaped superconducting magnet versus time.

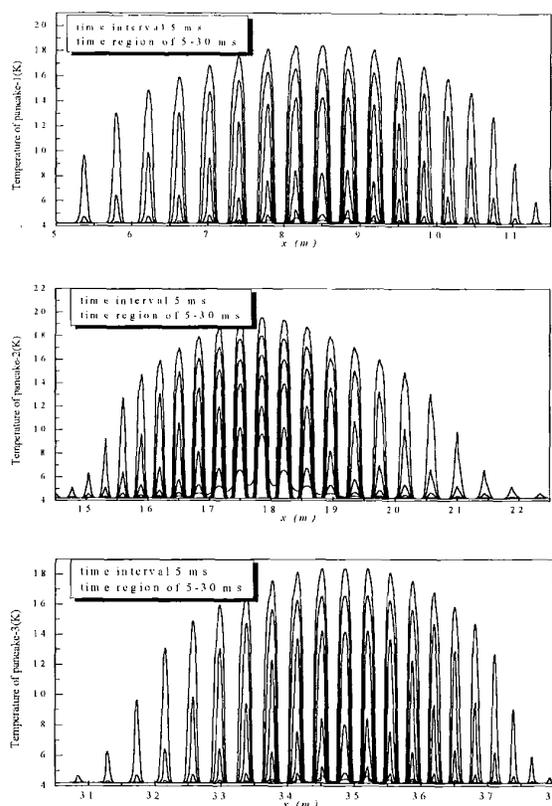


Fig. 3 Profiles of temperature of 3-pancake-shaped superconducting magnet versus space coordinate.

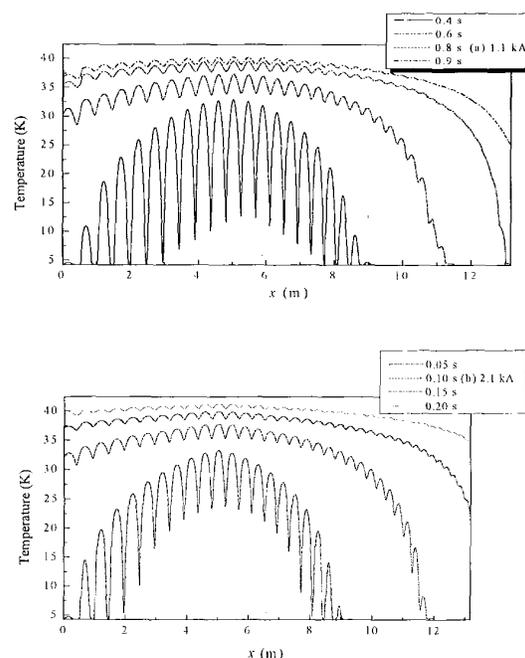


Fig. 4 Temperature distribution of 1-pancake-shaped magnet.

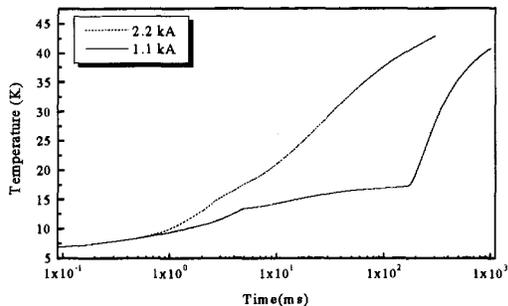


Fig. 5 Hot-spot temperature rise of 1-pancake-shaped magnet versus time for operating currents of 1.1 and 2.1 kA and field of 8.5 T.

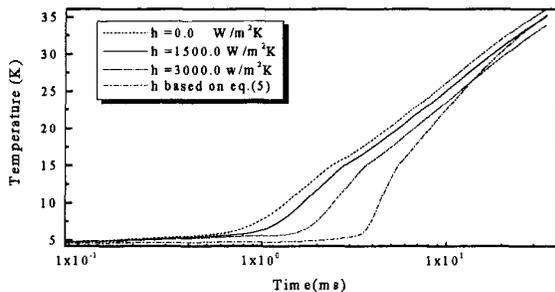


Fig. 6 Hot spot temperature rise of 1-pancake-shaped magnet versus time for the various heat transfer coefficients.

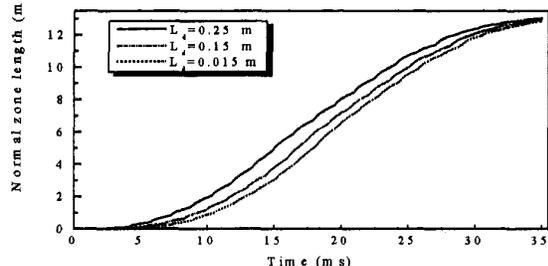


Fig. 7 Normal zone length of 1-pancake-shaped magnet versus time.

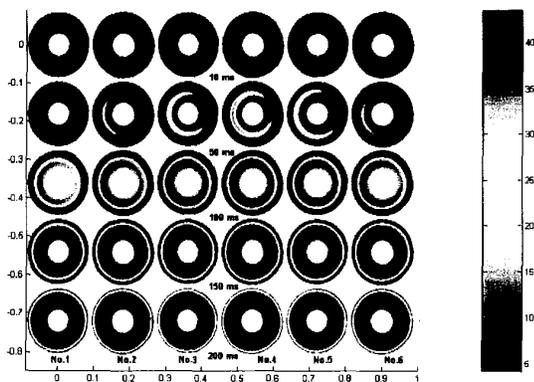


Fig. 8 Temperature distribution of 6-pancake-shaped magnet during the disturbance located at 16<sup>th</sup> of pancake No.4 (Unit of temperature in bar is K).

The disturbance length can influence on the normal zone propagation velocity. Fig. 7 shows the simulation results for the 1-pancake-shaped magnet under the background field of 8.5 T and operating current of 3 kA. The disturbance length and duration time are 0.015, 0.15, 0.25 m and 5 ms, respectively. The longer disturbance length has a higher normal zone propagation velocity. The initial quench region of the disturbance length of 0.25 m is over than that of 0.015 m. The larger quench region results in higher transverse heat flux through layers and pancakes. The fast increasing transverse generates the adjacent layers and pancakes quench.

The influence of the self-field of magnet on the normal zone propagation is studied for the 6-pancake-shaped superconducting magnet with the disturbance located at 16<sup>th</sup> layer of No.4 pancake. The external field is zero. The disturbance length and duration time are 0.15 m and 5 ms, respectively and operating current of 2.8 kA. The inner radius, outer radius and height of the magnet are 30 cm, 85 cm and 3.0 cm, respectively. The parameters of tape of  $Nb_3Sn$  are shown in Table-I. Fig.8 illustrates the profile of temperature distribution for the 6-pancake-shaped superconducting magnet system for the  $t = 10, 50, 100, 150, 200$  ms. At 10 ms, No.4 is in the quench state, and the adjacent pancakes No.3 and No.5 are still in the superconducting state. At  $t = 50$  ms, No.2, No.3, No.5 and No.6 start to quench. At  $t = 100$  ms all the pancakes are in the normal state for the inner layers because they are located at the high field region. At  $t = 150$  ms, all pancakes are at the normal state. From the Fig. 8, the self-field results in fast quench propagation velocity along radius, and the quench of the inner layers is faster than that of the outer layer.

#### IV. CONCLUSIONS

The quasi-three-dimensional model can simulate quench process in pancake-shaped superconducting magnet system. The moving mesh finite volume method is suitable to solve the moving boundary problem. The simulation results of the pancake-shaped superconducting magnet show : The insulation thickness of superconducting wire can influence on the hot-spot temperature and normal zone propagation velocity. The high operating current of magnet accelerates the normal zone propagation. Comparing the constant heat transfer and the transient heat transfer of liquid helium varied from the nucleate boiling to the film boiling, the transient heat transfer can lead to the lower hot-spot temperature rise in the initial time and then high hot-spot temperature in the film boiling region.

#### REFERENCES

- [1] L. Dresner, Stability of Superconductors, 1995 Plenum Press..
- [2] S. Li, L. Petzold, "Moving mesh methods with upwinding schemes for time-dependent PDEs," J.of Computational Physics 131(1997)368.
- [3] L. Bottura, O.C. Zienkiewicz, "Quench analysis of large superconducting magnets," Cryogenics 32(1992)659-667.
- [4] W.Z. Huang, Y. Ren and R.D. Russell, "Moving mesh methods based on moving mesh partial differential equations," J. of Computational Physics 113(1994)279.